

INFLUENCE OF MULTIPLE TAKER-IN SYSTEM UPON TENSILE PARAMETERS OF COTTON YARN

Sheikh Muhammad Nawaz, Babar Shahbaz, and Nasrullah Khan

Department of Fibre Technology, University of Agriculture, Faisalabad, Pakistan

(Received 11 August 1999; accepted 3 July 2001)

The study was aimed at comparing the effect of the conventional high production card with a modified card equipped with multiple taker-in system upon tensile parameters (viz., single yarn strength, elongation and rupture per kilometer) of 24^s cotton yarn. The quality of yarn was significantly improved by the modified system. Thus by modifying and updating the webfeed system, an older carding machine can be made to produce yarn of impressive quality.

Key words: Carding, Multiple taker-in system, Tensile parameters, Yarn.

Introduction

Whenever the question is raised of how to achieve high quality in spinning preparations, the cards will be the key machine. It is in this machine that the most important characteristic data of significance to quality in the subsequent spinning process is established. One of the most effective ways of increasing the productivity of a card machine is the enlargement of the pre-carding element. It is well known that an enlarged taker-in assembly extracts a large volume of waste, which is advantageous with regard to improving web and yarn quality (Ghaffar 1990; Irshad 1994). The performance of the cylinder flats assembly and in the final analysis, the quality of the card web depends on the efficiency of the taker-in separating the flocks into individual fibres and of eliminating extraneous matter and neps (Leifeld 1996).

The multiple taker-in system provides a vehicle for the out class effectiveness of the "flat-cylinder" system to the point of full development. In the carding zone, carding results are determined by clothing fineness and condition, by cylinder speed, and by the narrowness of the gap between the flat and cylinder clothing points (Schlichter and Leifeld 1996).

The main effect of the new precarding unit, comprising three opening and cleaning rollers instead of one taker-in roller is not as is generally assumed i.e. the additional cleaning effect, but the possibility of achieving better carding conditions at the cylinder through correctly staged opening. This study is targeted to compare the effect of an existing high production card with that of the modified card (equipped with multiple taker-in system) upon the tensile parameters of 24^s cotton yarn.

This research work was conducted at the Department of Fibre Technology, University of Agriculture, Faisalabad and at the Aamer Cotton Mills (Ltd.), Jumberkhurd, Distt. Kasur, Pakistan, under the standard atmospheric conditions (i.e., 20±2°C temperature and 65±2 % relative humidity). Cotton variety MNH-93 having 27.06 millimeter length, 4.5 micronaire value, 27 gram/ten strength, 48.62 percent uniformity ratio and 82.55 percent maturity was selected for the study.

The material was fed through the chute feed system at the same rate to the following cards:

A₁ = Modified card, A₂ = Conventional card.

The modified card was equipped with multiple taker-in system (consisting of three additional rollers as shown in Fig 1).

The specifications of these additional rollers are as under:

| | 1st roller | 2nd roller | 3rd roller |
|------------------------------|--------------|--------------|---------------|
| Diameter | 172.5 mm | 172.5 mm | 172.5 mm |
| Wire angle | 17° | 20° | 20° |
| Points per inch ² | 36 | 162 | 205 |
| Teeth length | 5.0 mm | 5.0 mm | 8.0 mm |
| Speed | 621-1373 rpm | 800-1730 rpm | 1066-2488 rpm |

The following speeds of both carding machines were changed to study their effects.

a. Taker-in speeds (B)

B₁ = minimum speed of taker-in; B₂ = maximum speed of taker-in


b. Cylinder speeds (C)

C₁ = 450 rpm; C₂ = 500 rpm

c. Doffer speeds (D)

D₁ = 75 ypm (30 rpm); D₂ = 100 ypm (40 rpm); D₃ = 125 ypm (50 rpm); D₄ = 150 ypm (60 rpm)

*Author for correspondence

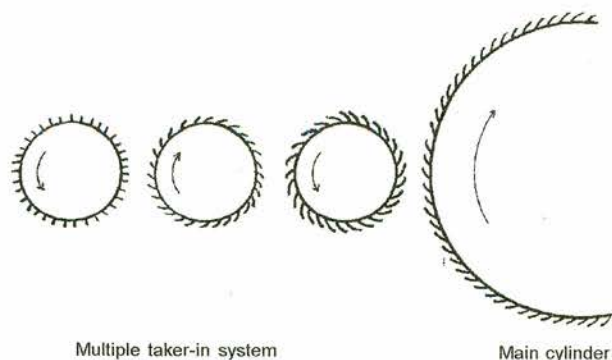

Multiple taker-in system

Main cylinder

Fig 1. Multiple taker-in system at card.

The sliver samples of both cards were prepared at different treatments of taker-in, cylinder and doffer speed combinations (Table 1). The sliver samples of 60 in/yd of both conventional and modified card were then processed on a drawing and simplex machine and finally the yarn of 24^s English count was prepared using a Toyoda ring frame. The sliver samples obtained from both cards were processed on the same drawing, simplex and spinning machines.

Following characteristics of yarn were determined.

Single yarn strength was measured by "Uster Tensorapid Tester 111" according to the ASTM standards (1968).

Yarn elongation was measured by "Uster Tensorapid Tester 111". The procedure was adopted as laid down in its operational manual (1968).

Table 1
Treatment combinations

| Treatments | Combinations of taker-in, cylinder and doffer speeds |
|------------|--|
| 1 | B ₁ C ₁ D ₁ |
| 2 | B ₁ C ₁ D ₂ |
| 3 | B ₁ C ₁ D ₃ |
| 4 | B ₁ C ₁ D ₄ |
| 5 | B ₁ C ₂ D ₁ |
| 6 | B ₁ C ₂ D ₂ |
| 7 | B ₁ C ₂ D ₃ |
| 8 | B ₁ C ₂ D ₄ |
| 9 | B ₂ C ₁ D ₁ |
| 10 | B ₂ C ₁ D ₂ |
| 11 | B ₂ C ₁ D ₃ |
| 12 | B ₂ C ₁ D ₄ |
| 13 | B ₂ C ₂ D ₁ |
| 14 | B ₂ C ₂ D ₂ |
| 15 | B ₂ C ₂ D ₃ |
| 16 | B ₂ C ₂ D ₄ |

B=Taker-in speed, C=Cylinder speed and D=Doffer speed

The rupture per kilometer is actually tensile strength of yarn in grams per tex. RKM was calculated by applying the following formula.

$$\text{RKM (g/tex)} = \text{Single yarn strength} \times 0.00169 \times \text{count (Ne)}$$

The data obtained were analyzed statistically as suggested by Steel and Torrie (1980), on M. Stat Micro computer statistical Program devised by Freed (1992).

The individual comparison of means by taking five replication of each trademark (Table 2, Fig 2) reveals that at modified card single yarn strength of 344.70g is recorded as 344.00g for conventional card and these values differ non-significantly from each other. The results indicate that the multiple taker-in system did not influence the single yarn strength. This is due to the fact that subsequent processes in spinning after carding amend the quality characteristics of the yarn. Schlichter and Leifeld (1996) stated that improved pre-opening of cotton fibres before the cylinder can positively influence the quality of yarn.

For taker-in and doffer speeds, significant differences were recorded in the mean values of single yarn strength while cylinder speed displayed a non-significant effect (Table 2). The combination of power speed of taker-in and D₂ (100 rpm) speed of doffer are thus, evident as better performing speeds for producing higher values of single yarn strength. Previous researcher Nozaki (1968) also recorded improved yarn strength at lower taker-in speed. Present results for the doffer speed variable deviate from the findings of Nozaki (1968) that strength of yarn depends upon neither the production rate nor doffer speed. Variation in the results may be due to many factors such as quality of raw material and machine settings. Douglas (1991) reported that modern high speed machinery has resulted in an overall quality improvement.

The results of the present work deviate from those recorded by Farooqi (1992) as 353.25-388.42 g (range) for single yarn strength of 24^s yarn of MNH-93 cotton variety. The variation in the results may be due to the difference in quality of raw material, machine settings, material handling, etc.

It is apparent from Fig 3 and the comparison of individual means (Table 3) that the modified card equipped with multiple taker-in system produces high percentage of yarn elongation (3.82%) as compared to 3.70 percent for conventional card. Both of these values differ significantly from one another. This improvement might be attributed to the attachment of additional roller (multiple taker-in system) at modified card. Artz and Maidel (1983) mentioned that the elongation of a yarn depends on the amount of work done on the fibres during carding. Schlichter and Leifeld (1996) stated that gentle opening of the material by the web feed results in improved dynamometric yarn values (yarn strength and elongation).

Table 2
Individual comparison of mean values for single yarn strength

| Machine means | | Taker-in speed means | | Cylinder speed means | | Doffer speed means | |
|---------------|---------|----------------------|---------|----------------------|---------|--------------------|---------|
| A1 | 344.70a | B1 | 347.03a | C1 | 343.70a | D1 | 338.55b |
| A2 | 344.00a | B2 | 341.40b | C2 | 344.40a | D2 | 351.52a |
| | | | | | | D3 | 340.24b |
| | | | | | | D4 | 347.09a |

Any two means not sharing common letters differ significantly at P=0.05

Table 3
Individual comparison of mean values for yarn elongation

| Machine means | | Taker-in speed means | | Cylinder speed means | | Doffer speed means | |
|---------------|-------|----------------------|-------|----------------------|-------|--------------------|--------|
| A1 | 3.82a | B1 | 3.79a | C1 | 3.73b | D1 | 3.80a |
| A2 | 3.70b | B2 | 3.73a | C2 | 3.79a | D2 | 3.80a |
| | | | | | | D3 | 3.73ab |
| | | | | | | D4 | 3.71b |

Any two means not sharing common letters differ significantly at P=0.05

With regard to carding parameters, significant differences in the mean values are observed for cylinder and doffer speeds whereas a non-significant effect is recorded for taker-in speed. Previously many researchers (Rusca 1970; Ahmad 1991) reported that the increase in yarn elongation, requires necessitates increase in twist and consequent losses in strength and production. They further stated that fine yarn has higher elongation variability than coarse yarn. The tenacity and elongation properties of single yarn were related directly to the fibre elongation of cotton from which they were spun.

The overall range of yarn elongation percentage is observed as 3.70 to 3.82 percent. The present results deviate from the results described by Farooqi (1992) noted the yarn elongation percentage of 24^s yarn of MNH-93 cotton variety

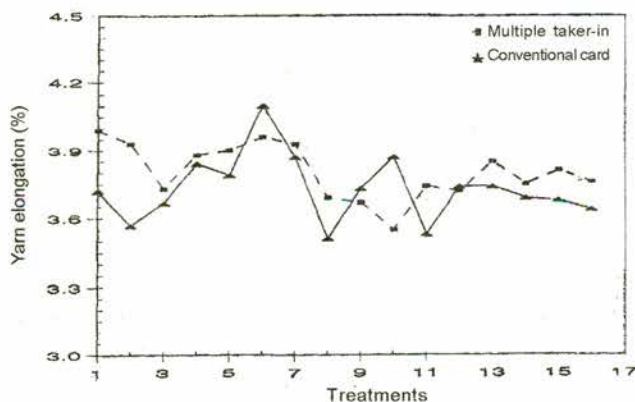


Fig 3. Comparison of two machines at different treatments for yarn elongation.

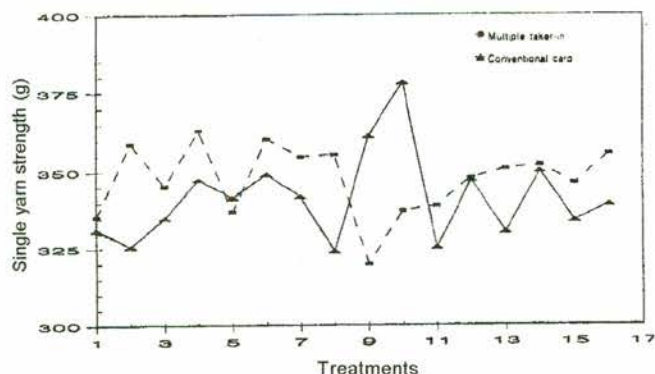


Fig 2. Comparison of two machines at different treatments for single yarn strength.

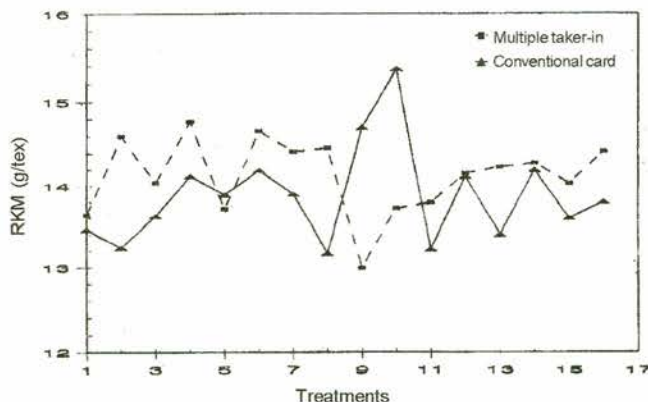


Fig 4. Comparison of two machines at different treatments for RKM.

Table 4
Individual comparison of mean values for RKM

| Machine means | | Taker-in speed means | | Cylinder speed means | | Doffer speed means | |
|---------------|--------|----------------------|--------|----------------------|--------|--------------------|--------|
| A1 | 14.00a | B1 | 14.12a | C1 | 13.97a | D1 | 13.75b |
| A2 | 13.99a | B2 | 13.87b | C2 | 14.02a | D2 | 14.28a |
| | | | | | | D3 | 13.82b |
| | | | | | | D4 | 14.13a |

Any two means not sharing common letters differ significantly at P=0.05

in the range of 3.91 to 5.42 percent. Many factors like quality of raw material, material handling, machine settings, etc., are involved for the variation in results.

The comparison of individual means presented in Table 4 indicates the non-significant effect of modified card (equipped with multiple taker-in system) on RKM value of yarn (Fig 4). This is due to the fact that subsequent processes in spinning after carding amend the quality characteristics of yarn.

As far as carding parameters are concerned, significant differences in the mean values are recorded for taker-in and doffer speeds while cylinder speed depicts non-significant effect for RKM value of 24^s yarn. The best performance of lower speed of taker-in (B_1) and D_2 (100 rpm) speed of doffer is thus, evident from the results (Table 4). The present results are in line with the results of Farooqi (1992) who recorded RKM value of 24^s yarn of MNH-93 cotton variety in the range of 13.10 to 15.55 g/tex.

Conclusion

The following conclusions are drawn from the present investigations.

1. In the comparison of conventional high production and multiple taker-in system card, results showed that by modifying and updating the taker-in system, yarn of impressive quality can be produced.
2. Lower speed of taker-in (B_1), higher speed of cylinder (C_2) and D_2 (100 rpm) of doffer is accompanied better performance for yarn tensile parameters.

References

Ghaffar A 1990 A comparative study of conventional card machine and a modified card with an extra roller under taker-in. MSc thesis, Department of Fiber Technology

- University of Agriculture, Faisalabad.
- Irshad R 1994 Effect of control roller attachment at taker-in on cotton carding process. MSc thesis, Department of Fiber Technology University of Agriculture, Faisalabad.
- Leifeld F 1996 Meeting the challenge of the future with holistic solutions to complex problems. Paper presented at the Achener Textiltagung 1996, Aachen.
- Schlichter S, Leifeld F 1996 The new dimension in cards. Paper presented at the Beltwide Cotton Conference, Nashville, Tennessee, USA.
- Nozaki C 1968 How the quality of cotton yarn processed by a high production card is affected by its taker-in & doffer speed. *J. Textile Mach Society of Japan* **14**(5) 137-142.
- ASTM 1968 Tentative method of test for single yarn strength. ASTM Designation D: 2256-66 Amer. Soc. for testing materials. 34th ed Part 33. Philadelphia.
- Steel R G D, Torrie J H 1980 *Analysis of Variance Principles and Procedure of Statistics*. McGraw Hill Book Koga, Kosha Ltd Tokyo Japan 137-233.
- Fareed R D O 1992 *M-Stat Micro Computer Statistical Program*. Michigan State University of Agriculture. University of Norway 324B. Agriculture Hall East Lausing, Michigan Lausing, USA.
- Douglas K 1991 Relation between fibre and the yarn. *Uster News Bulletin*, No.36, Zellweger Ltd. 8610-Uster (Switzerland), 26-27.
- Artz P, Maidel H 1983 *Inst itur fur Textile-und verfahrenstechnik Derkendrat*, Germany.
- Rusca R A 1994 Cotton fibre properties. Southern regional laboratories. New Orleans. *Cotton Growing Review* **47** 206-216.
- Ahmad M M 1991 Assessment of cotton. *Textile and Leather Rev* 44-46.
- Farooqi M M 1992 MSc thesis, Department of Fiber Technology, University of Agriculture, Faisalabad.